

Relaxation of Hot Quasiparticles in a d -Wave Superconductor

P. C. Howell,¹ A. Rosch,¹ and P. J. Hirschfeld²

¹*Institut für Theorie der Kondensierten Materie, Universität Karlsruhe, 76128 Karlsruhe, Germany*

²*Department of Physics, University of Florida, Gainesville, FL 32611-8440, USA*

(Dated: February 2, 2008)

Motivated by recent pump-probe experiments we consider the processes by which “hot” quasiparticles produced near the antinodes of a d -wave superconductor can relax. We show that in a large region of momentum space processes which break Cooper pairs are forbidden by energy and momentum conservation. Equilibration then occurs by scattering with thermal quasiparticles: Umklapp scattering is exponentially suppressed at low temperatures, but small-angle scattering leads to power-law behavior. By solving the Boltzmann equation analytically we make detailed predictions for the temperature and intensity dependence of these processes, which we compare with experiment.

PACS numbers: 74.25.Gz, 78.47.+p, 74.72.-h

Introduction.—Despite intensive effort for more than a decade, no consensus exists on the form and origin of the effective electron-electron interaction leading to pairing in the cuprate superconductors. Furthermore, although it is generally agreed that the superconducting state has d -wave symmetry, many properties of the Bogoliubov quasiparticle (QP) excitations are not well understood [1]. In conventional superconductors, the study of non-equilibrium QP relaxation was used successfully to extract information on residual particle-particle interactions, as well as to pin down QP and phonon lifetimes (for a review, see Ref. [2]). The typical time-resolved experiment is a measurement of the change in the system’s dielectric constant as a function of time following a pump pulse which creates a non-equilibrium QP distribution. The excited QPs decay to equilibrium over a series of timescales involving several steps, including at least: (i) a cascade of pair production until a quasi-equilibrium is reached between “hot” QPs of roughly the gap energy Δ_0 and phonons of energy $2\Delta_0$, and (ii) slow recombination of QPs into Cooper pairs. The timescales involved in step (i) are $\mathcal{O}(\text{ps})$, but can be much longer in step (ii) [$\mathcal{O}(\text{ns}-\mu\text{s})$] since energy is continually exchanged between the electron and phonon systems until heat is removed at the sample surfaces; this long decay is sometimes referred to as the “phonon bottleneck”. These two rates were clearly identified in, for example, recent pulsed synchrotron measurements on Pb [3].

A priori, several differences are to be expected in the cuprate superconductors. The very strong interactions in the normal state and the larger gap scale Δ_0 suggest that electron-electron rather than electron-phonon scattering is the dominant relaxation mechanism. Furthermore, the gap anisotropy and the equilibration with thermal QPs at the nodes leads to a new type of slow decay, which we call the “antinodal bottleneck”. This is the inability of antinodal QPs to decay rapidly by pair-breaking while simultaneously satisfying energy and momentum conservation, due to the large difference in velocities at the nodal and antinodal points of the Fermi surface. (This

idea has also been proposed by Orenstein [4].)

Although several recent experiments on the cuprates have probed the decay of non-equilibrium QP populations in time [5, 6, 7, 8, 9, 10, 11, 12], their methods and results differ considerably and it is not clear yet whether a consistent interpretation can be extracted. A short relaxation process $\mathcal{O}(1-10 \text{ ps})$ has indeed been identified [6, 7, 8, 9] in experiments with pump pulse energy much greater than the gap scale. In addition, a much longer component $\mathcal{O}(10 \mu\text{s})$ component has been observed [5] and identified with a recombination bottleneck. Recently, however, Segre *et al.* [10] pointed out that the early relaxation component in their measurements on ortho-II YBCO_{6.52} single crystals was strongly T and intensity dependent, and in the limit of weak intensity they fitted it to a T^3 law. At low T , this “slow” component was of order hundreds of ps, but still many orders of magnitude shorter than that seen in Ref. [5].

Here we present a theory of the single aspect of the complicated non-equilibrium physics of pump-probe experiments most peculiar to the d -wave superconductor, namely the mechanism intermediate between steps (i) and (ii) whereby hot QPs scatter through the antinodal bottleneck before recombination (processes on longer timescales have been discussed in Ref. [13]). Within a model where QPs are scattered by a simple local interaction, we show that at high T there is a fast relaxation due to Umklapp scattering, but below some crossover temperature relaxation is dominated by diffusion in momentum space along the Fermi surface from the antinode to the nodes. This idea is a momentum-space analog of real-space “QP traps” in conventional superconductors [14], in the sense that there is an intermediate stage of relaxation in which QPs diffuse to a region of lower gap.

Antinodal bottleneck.—The (extrapolated) relaxation rate of QPs of energy $\sim \Delta_0$ vanishes as $T \rightarrow 0$ in the experiment of Segre *et al.* [10], implying both that the Ortho II sample is extremely pure, so that impurities may be neglected, and that pair-breaking processes are forbidden. We now show that the latter effect is a simple

consequence of the requirements of energy and momentum conservation. We assume a d -wave order parameter $\Delta_{\mathbf{k}} = \Delta_0 \cos 2\theta$ over a Fermi surface parameterized by θ . In the coordinate systems of Fig. 1(a) the BCS dispersion relation can then be expanded for momenta $\mathbf{k}$ near the antinode as $E_{\mathbf{k}} = \Delta_{\mathbf{k}} + 2k^2 E_F^2 / \Delta_{\mathbf{k}}$ and for momenta $\mathbf{p}$ near the node as $E_{\mathbf{p}} = 2\sqrt{E_F^2 p_{\perp}^2 + \Delta_0^2 p_{\parallel}^2}$ (with $k_F=1$).

For simplicity, consider an antinodal QP exactly on the Fermi surface, which for small transferred momentum $\mathbf{q}$ must scatter parallel to the Fermi surface, $\phi \approx \frac{\pi}{2} - \theta$ [see Fig. 1(a)]; the energy lost is then $E_{\text{lost}} \approx 2q\Delta_0 \sin 2\theta$. The minimum energy required to break a Cooper pair, *i.e.*, to create two nodal QPs with momenta $\mathbf{p}$ and $-\mathbf{p}-\mathbf{q}$, is $2qE_F \sin |\frac{\pi}{4} - \theta|$, which for $|\frac{\pi}{4} - \theta| > \Delta_0/E_F$ is larger than E_{lost} . More generally, pair-breaking cannot occur for $k \lesssim 1/\sqrt{2}(\Delta_0/E_F)^2 \cos^2 2\theta$, where k is the distance from the Fermi surface. The origin of this bottleneck is that the velocity of the antinodal QP is much less than nodal velocities. While the above analysis neglects Umklapp scattering, including it only modifies the picture quantitatively: the bottleneck for pair-breaking remains but its size now depends on details of the Fermi surface.

How, then, can a hot QP relax, trapped as it is in the bottleneck? It could be scattered by phonons, impurities, various electronic collective excitations, thermal (nodal) QPs or other hot (antinodal) QPs. For the creation of phonons there is an analogous bottleneck, although scattering from thermally excited phonons is possible. We now investigate in detail the consequences of scattering from thermal QPs; contributions from other hot QPs can be separated by their dependence on the laser intensity (see below). While our calculation includes only QP-QP scattering, we expect qualitatively similar results for scattering from (non-critical) spin fluctuations, as has been shown to be the case for the optical conductivity up to a phenomenological prefactor [15, 16].

In the spirit of a Fermi liquid approach we assume the existence of well-defined QPs, $d_{\mathbf{k}\uparrow}^\dagger = u_{\mathbf{k}} c_{\mathbf{k}\uparrow}^\dagger - v_{\mathbf{k}} c_{-\mathbf{k}\downarrow}$, where $u_{\mathbf{k}}$ and $v_{\mathbf{k}}$ are the usual Bogoliubov coefficients. At low T two-particle processes dominate, parameterized by the following Hamiltonian:

$$\mathcal{H} = \sum \left[V_{2-3}^{\text{pp}} r_{12} r_{34} d_{4\uparrow}^\dagger d_{3\downarrow}^\dagger d_{2\downarrow}^\dagger d_{1\uparrow}^\dagger + V_{2+1}^{\text{pb}} \tilde{r}_{12} r_{34} d_{4\uparrow}^\dagger d_{3\downarrow}^\dagger d_{2\sigma}^\dagger d_{1\sigma} + V_{2+1}^{\text{qq}} r_{12} r_{34} d_{4\sigma}^\dagger d_{3\bar{\sigma}}^\dagger d_{2\bar{\sigma}} d_{1\sigma} + V_{2-3}^{\text{qq}} \tilde{r}_{14} \tilde{r}_{23} d_{4\sigma}^\dagger d_{3\sigma'}^\dagger d_{2\sigma'} d_{1\sigma} + \text{H.c.} \right], \quad (1)$$

where $i \equiv \mathbf{k}_i$, $r_{ij} = u_i v_j + v_i u_j$, $\tilde{r}_{ij} = u_i u_j - v_i v_j$ and the sum conserves crystal momentum. We assume that the effective interactions V are only weakly dependent on momentum (this is not justified if long-ranged spin-fluctuations are important). Hot QPs predominantly relax by scattering from thermal QPs, as expressed by the last two terms; energy conservation forbids leading con-

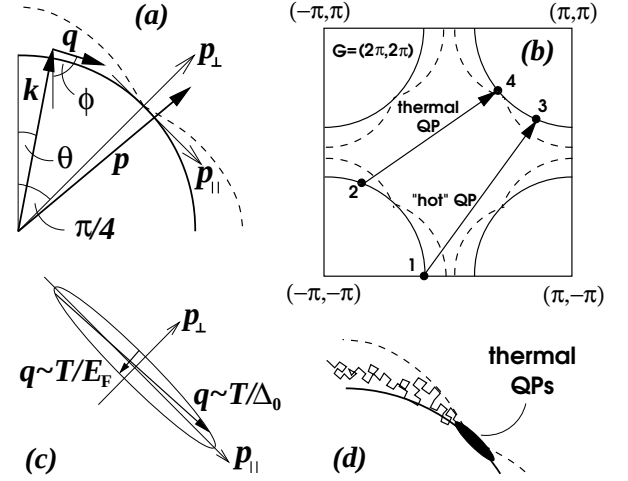


FIG. 1: (a) Coordinate systems for the QP momenta (heavy line: Fermi surface, dashed line: superconducting gap). Momenta $\mathbf{k}$ near the antinodes are given in polar coordinates $(k_F + k, \theta)$ and momenta $\mathbf{p}$ near the nodes in Cartesian coordinates $(p_{\perp}, p_{\parallel})$ relative to the node. The antinodal QP scatters from $\mathbf{k}$ to $\mathbf{k} + \mathbf{q}$, where $\mathbf{q} = (q, \phi)$ is in polar coordinates. (b) A typical Umklapp scattering process. (c) Typical magnitudes of the momentum transfer for scattering perpendicular and parallel to the nodal Fermi surface. (d) Schematic picture of diffusion of a hot antinodal QP towards the node.

tributions from the first term, while the bottleneck discussed above blocks pair-breaking processes from the second term. The BCS coherence factors $r_{ij}, \tilde{r}_{ij}$ are of order unity for the relevant processes and so will be neglected.

There are two types of scattering of hot QPs from thermal QPs, distinguished by their typical momentum transfer. We first discuss Umklapp scattering, which involves large transferred momenta, $q \sim k_F$, as illustrated in Fig. 1(b). A hot QP undergoing Umklapp and subsequent pair-breaking scattering can reach the node in a small number of scattering events. However, due to kinematic constraints such scatterings are only possible if the thermal QP is some minimum angle away from the node and therefore has a minimum energy Δ_U . Accordingly, the corresponding scattering rate is exponentially suppressed. Using Fermi's golden rule we obtain

$$\frac{1}{\tau_U} \approx M_{\text{qq}} \frac{(2\pi\Delta_U T)^{3/2}}{\Delta_0/E_F} e^{-\Delta_U/T}, \quad M_{\text{qq}} = \frac{2\pi V_{\text{qq}}^2 a^4}{\hbar(2\pi\hbar v_F)^4}, \quad (2)$$

where a is the lattice constant, v_F is the Fermi velocity and the size of $\Delta_U < \Delta_0$ depends on the details of the Fermi surface shape. An analogous Umklapp gap determines the momentum relaxation of nodal QPs [16] and hence the optical conductivity at low frequency.

At low T the second type of process becomes important: normal scattering, which we now show involves small momenta, $q \ll k_F$. For a given $\mathbf{q}$ the slow antinodal QP loses energy much less than $q\Delta_0$, so that the energy of the fast nodal QP changes little, $E_{\mathbf{p}} \approx E_{\mathbf{p}-\mathbf{q}}$. Therefore

the typical q depends on direction [see Fig. 1(c)], and is $q \approx 2p_{\parallel} \sim T/\Delta_0$ for scattering parallel to the Fermi surface at the nodes ($\phi \approx \frac{\pi}{4}$ and symmetry-related angles), and $q \approx 2p_{\perp} \sim T/E_F$ in perpendicular directions.

Since $q \ll k_F$, the hot QP experiences many collisions with the nodal QPs before it reaches the nodes, as sketched in Fig. 1(d). This has two important consequences: (i) the trajectory of the hot QP is diffusive in momentum space, and (ii) the hot QP thermalizes in the radial direction with the nodal QPs (see below). The typical momentum of a hot QP is thus determined by $E_{\mathbf{k}} - \Delta_0 \cos 2\theta \sim T$ and so $k \sim k_{\text{th}} = \sqrt{T\Delta_0}/E_F$.

Boltzmann equation.—To calculate the time τ_{θ} for a dilute distribution $g_{\mathbf{k}}(t)$ of antinodal QPs to reach the nodes we first consider the situation where the radial distribution of hot QPs lies entirely within the bottleneck, $k_{\text{th}} \ll (\Delta_0/E_F)^2$, which requires $T \ll \Delta_0^3/E_F^2$. We assume the nodal QPs are always in local thermal equilibrium, as τ_{θ}^{-1} will turn out to be much slower than the nodal relaxation rate $\sim M_{\text{qq}}T^3E_F^2/\Delta_0^2$. Linearizing in $g_{\mathbf{k}}$ the Boltzmann equation reads

$$\frac{\partial g_{\mathbf{k}}}{\partial t} = \int d\mathbf{q} \left[g_{\mathbf{k}-\mathbf{q}} G_{\text{qq}}(\mathbf{q}, \varepsilon_{\mathbf{k}-\mathbf{q}, \mathbf{q}}) - g_{\mathbf{k}} G_{\text{qq}}(\mathbf{q}, \varepsilon_{\mathbf{k}, \mathbf{q}}) \right], \quad (3)$$

$$G_{\text{qq}}(\mathbf{q}, \varepsilon) = M_{\text{qq}} \int d\mathbf{p} f_{\mathbf{p}} (1 - f_{\mathbf{p}-\mathbf{q}}) \delta(\varepsilon_{\mathbf{p}-\mathbf{q}} + \varepsilon). \quad (4)$$

Here $f_{\mathbf{p}}$ is a Fermi function, $\varepsilon_{\mathbf{k}, \mathbf{q}} = E_{\mathbf{k}} - E_{\mathbf{k}+\mathbf{q}}$ is the energy transfer, and G_{qq} is the integral over momenta near all four nodes of QP–QP scattering processes.

Since we expect the hot QPs to thermalize in the radial direction we make the transformation

$$g_{\mathbf{k}}(t) = \frac{C_{\mathbf{k}}(t)}{h_{\theta_{\mathbf{k}}}} e^{-\beta E_{\mathbf{k}}}, \quad h_{\theta_{\mathbf{k}}} = \int (1+k) dk e^{-\beta E_{\mathbf{k}}}, \quad (5)$$

where $C_{\mathbf{k}}(t)$ is a smooth function of $\mathbf{k}$ to be determined. [The factor of $(1+k)$ comes from the use of polar coordinates.] Using detailed balance and (5), the Boltzmann equation now takes the form

$$\frac{1}{h_{\theta_{\mathbf{k}}}} \frac{\partial C_{\mathbf{k}}}{\partial t} = \int d\mathbf{q} G(\mathbf{q}, \varepsilon_{\mathbf{k}, \mathbf{q}}) \left[\frac{C_{\mathbf{k}+\mathbf{q}}}{h_{\theta_{\mathbf{k}+\mathbf{q}}}} - \frac{C_{\mathbf{k}}}{h_{\theta_{\mathbf{k}}}} \right]. \quad (6)$$

If the hot QPs are close to *radial* equilibrium we expect $C_{\mathbf{k}}$ to depend only weakly on k and therefore expand it as $C_{\mathbf{k}}(t) = C_{\theta_{\mathbf{k}}}^0(t) + (k - \langle k \rangle) C_{\theta_{\mathbf{k}}}^1(t) + \dots$, where $\langle k \rangle = h_{\theta_{\mathbf{k}}}^{-1} \int (1+k) dk k e^{-\beta E_{\mathbf{k}}}$ such that $\int d\mathbf{k} g_{\mathbf{k}}(t) = \int d\theta C_{\theta}^0(t)$. The equation for C_{θ}^0 can then be projected out from (6) by integrating over radial directions. Since $q \partial_{\theta} (C_{\theta}^0/h_{\theta}) \ll C_{\theta}^0/h_{\theta}$ we can perform a gradient expansion, leading to (for $\theta \ll \frac{\pi}{4}$)

$$\frac{\partial}{\partial t} \left[\frac{C_{\theta}^0(t)}{h_{\theta}} \right] = \left[F\theta \frac{\partial}{\partial \theta} + D \frac{\partial^2}{\partial \theta^2} \right] \frac{C_{\theta}^0(t)}{h_{\theta}}, \quad (7)$$

$$F = \frac{1}{\theta} \int d^2\mathbf{q} dk \frac{e^{-\beta E_{\mathbf{k}}}}{h_{\theta}} q \sin(\theta + \phi) G_{\text{qq}}(\mathbf{q}, \varepsilon_{\mathbf{k}, \mathbf{q}}), \quad (8)$$

$$D = \int d^2\mathbf{q} dk \frac{e^{-\beta E_{\mathbf{k}}}}{h_{\theta}} \frac{q^2 \sin^2(\theta + \phi)}{2(1+k)} G_{\text{qq}}(\mathbf{q}, \varepsilon_{\mathbf{k}, \mathbf{q}}). \quad (9)$$

The main contribution is from $\phi \approx \frac{\pi}{4}$ leading to “zig-zag” diffusion in momentum space [see Fig. 1(d)], and hence

$$F \approx \frac{7\pi^5}{80} \frac{M_{\text{qq}}T^4E_F^2}{\Delta_0^3}, \quad D = F \frac{T}{4\Delta_0}. \quad (10)$$

We have dropped terms in C_{θ}^i ($i \geq 1$) on the right-hand side of (7) since they decay faster than C_{θ}^0 (see below).

As $F/D = 4\Delta_0/T$ we can rewrite (7) for $\theta \ll \frac{\pi}{4}$ as

$$\partial_t C_{\theta}^0 = -F \partial_{\theta} (\theta C_{\theta}^0) + D \partial_{\theta}^2 C_{\theta}^0. \quad (11)$$

Now D can be identified as the diffusion constant in momentum space, while F parameterizes the force driving hot QPs towards the nodes. We emphasize that the forms of (7) and (11) are completely determined by detailed balance, local conservation of the number of hot QPs and symmetry under $\theta \rightarrow -\theta$. The Boltzmann distribution $C_{\theta}^0 \propto h_{\theta}$ obviously solves (7), while the conservation of the number of hot QPs, $N_{\text{hot}} = \int d\theta C_{\theta}^0(t)$, is manifest in (11); the equivalence of (7) and (11) fixes F/D .

For an initial Gaussian distribution of width α the solution to (11) is a Gaussian of width $\sigma(t)$, where $\sigma^2(t) = (2D/F + \alpha^2)e^{2Ft} - 2D/F$. For short times, $t \ll 1/F$, the motion is diffusive, $\sigma = 2\sqrt{Dt}$, while for $t \gg 1/F$ we obtain $\sigma \propto e^{Ft}$. The antinodal QPs reach the node after a time τ_{θ} such that $\sigma(\tau_{\theta}) \sim \pi/4$, and hence

$$1/\tau_{\theta} \sim F/\ln(\min[\sqrt{F/D}, \alpha^{-1}]) \sim M_{\text{qq}}T^4E_F^2/\Delta_0^3. \quad (12)$$

Details of the initial distribution only give log corrections.

To check the assumption of radial equilibrium we calculate perturbatively the evolution of the corrections $C_{\theta}^1(t), C_{\theta}^2(t), \dots$ using (6). Deviations from radial equilibrium decay rapidly, $\partial C_{\theta}^i/\partial t \approx -C_{\theta}^i/\tau_i$ where $\tau_i \lesssim \tau_{\theta} \Delta_0^2/E_F^2 \ll \tau_{\theta}$ for $i \geq 1$, and can therefore be neglected.

Higher temperatures.—We now consider higher temperatures, $\Delta_0^3/E_F^2 \ll T \ll \Delta_0^2/E_F$, where the upper limit comes from the neglect of curvature in the nodal dispersion $E_{\mathbf{p}}$. In this regime the typical antinodal velocity $4k_{\text{th}}E_F^2/\Delta_0 = 4E_F\sqrt{T/\Delta_0}$ is now large compared to the nodal velocity parallel to the Fermi surface, but still small compared to the perpendicular nodal velocity. This has two consequences. (i) Pair-breaking (and recombination) is now allowed, as $k_{\text{th}} \gg \Delta_0^2/E_F^2$, *i.e.* the QP is outside the bottleneck; in such a process one QP turns into three, of which two must reside at the nodes (due to energy and momentum conservation). (ii) Typical transferred momenta still turn to be small, for both pair-breaking and QP–QP processes, although now $q \sim \sqrt{T\Delta_0}/E_F$ for scattering parallel to the nodal Fermi surface (instead of $q \sim T/\Delta_0$ when $T \ll \Delta_0^3/E_F^2$).

All physical requirements which led to the form of (7), (11) and fixed the ratio F/D are therefore fulfilled: conservation of *antinodal* QPs, small momentum transfer and detailed balance (since both pair-breaking and recombination are possible). Generalizing (8), we find

$$1/\tau_{\theta} \approx (0.92M_{\text{qq}} + 0.67M_{\text{pb}}) \sqrt{T^5\Delta_0^3/E_F}, \quad (13)$$

with M_{pb} defined analogously to M_{qq} , Eq. (2).

Discussion.—We have shown that for vanishing laser intensity there are two relaxation mechanisms for hot QPs: Umklapp scattering from thermal QPs with an exponential relaxation rate (2), and normal scattering with a power-law rate (12, 13). While early experiments were fitted to a T^3 law [10], later results [4, 11] suggest activated behavior for the lowest measured temperature (down to 10 K), $\tau^{-1} \approx \gamma e^{-E_{act}/T}$, with $\gamma \approx 8 \times 10^{12} \text{ s}^{-1}$, $E_{act} \approx 100 \text{ K}$. This is consistent with the picture given above, where from (2) and (13) the crossover to $T^{5/2}$ behavior is expected to occur when $e^{-E_{act}/T} \sim T\Delta_0/E_F^2$, or $T \approx 8 \text{ K}$, assuming $\Delta_0 \approx 200 \text{ K}$ [17] and $E_F \approx 8\Delta_0$ [18]. The surprisingly low crossover scale $\sim 0.1E_{act}$ arises since many small-momentum scattering events are required for the hot QP to reach the nodes and therefore (13) is small. Note that the crossover from $T^{5/2}$ (13) to T^4 (12) is expected around $T \sim \Delta_0^3/E_F^2 \approx 1 \text{ K}$.

As a consistency check of our approach we now consider the absolute magnitude of the relaxation rate, for which we require M_{qq} in (2). Assuming that a similar matrix element appears in the optical conductivity, we can use the fit of Walker and Smith [16] to YBCO_{6.99} to find $M_{qq} \approx 2 \times 10^{17} \text{ eV}^{-3} \text{ s}^{-1}$. This gives $\tau_U \approx 1 \text{ ns}$ at $T = 20 \text{ K}$, to be compared to the experimental value of 0.03 ns. Given the possible momentum-dependence of M_{qq} , Fermi surface shape effects, the difference in doping in the two experiments and especially the uncertainty in E_{act} , this is not unreasonable agreement.

Within our model we can also estimate the intensity dependence of the scattering rate, which experimentally [10, 11] is given by $\tau_n^{-1} \approx c\rho$ almost independent of T , where ρ is the energy density deposited by the laser and $c \approx 1.2 \times 10^6 \text{ s}^{-1} \text{ J}^{-1} \text{ m}^3$. Assuming a uniform distribution of hot QPs on the Fermi surface, we use Fermi's golden rule to find $1/\tau_n \approx 8\pi M_{qq} n_{hot} (\hbar v_F)^4 \ln(E_F/\Delta_0) \Delta_0/E_F^2$, where n_{hot} is the (planar) density of hot QPs. With the above numbers, a comparison to the experiment would suggest that only $\sim 0.1\%$ of the deposited energy is used to create n_{hot} hot QPs each of energy $\sim \Delta_0$; equivalently, assuming 100% energy conversion, our predicted rates are a factor 10^3 too large. While a sizable fraction of the laser energy probably goes into the phonon system, we think this is unlikely to explain the discrepancy completely.

Conclusions.—Using BCS theory for d -wave superconductors we have calculated the electronic contribution to the relaxation of hot QPs. An analytical solution to the QP Boltzmann equation shows that small momentum scattering leads to a diffusive dynamics of antinodal QPs and associated power-law relaxation rates, unfortunately for $T < 10 \text{ K}$ which has not yet been investigated exper-

imentally. At higher T the relaxation is dominated by Umklapp scattering with large momentum transfer leading to exponential T dependence, consistent with experiments on ultra-clean samples. However, it is currently unclear whether our estimates for magnitudes of relaxation times are correct, and improvement will require a more complete understanding of the relation between the incident photon intensity and the number of hot QPs.

There are still many details and apparent discrepancies between the various non-equilibrium measurements on the cuprates which we cannot understand at present, and it is clear that more realistic physics must be incorporated to describe the evolution of the QP distribution over all timescales of interest, at different dopings, and in dirtier samples, as well as the dynamics of the order parameter. We believe nevertheless that the theoretical analysis of these experiments is worth pursuing since they potentially provide a window on the frequency and momentum dependence of the interactions responsible for superconductivity in these systems.

Acknowledgements. This work was supported by the Emmy Noether programme of the DFG and NSF-DMR 99-74396. The authors thank M. Eschrig, N. Gedik, R. Kaindl, P. Lemmens, J. Orenstein, D. J. Scalapino, M. Vojta and P. Wölfle for stimulating conversations.

-
- [1] N. E. Hussey, *Adv. Phys.* **51**, 1685 (2002).
 - [2] *Nonequilibrium Superconductivity*, edited by D. N. Langenberg and A. I. Larkin (North-Holland, New York, 1986).
 - [3] G. L. Carr *et al.*, *Phys. Rev. Lett.* **85**, 3001 (2000).
 - [4] J. Orenstein (private communication).
 - [5] B. J. Feenstra *et al.*, *Phys. Rev. Lett.* **79**, 4890 (1997).
 - [6] V. V. Kabanov *et al.*, *Phys. Rev. B* **59**, 1497 (1999).
 - [7] R. A. Kaindl *et al.*, *Science* **287**, 470 (2000).
 - [8] R. D. Averitt *et al.*, *Phys. Rev. B* **63**, 140502 (2001).
 - [9] M. L. Schneider *et al.*, *Europhys. Lett.* **60**, 460 (2002).
 - [10] G. P. Segre *et al.*, *Phys. Rev. Lett.* **88**, 137001 (2002); J. Demsar *et al.*, *Phys. Rev. Lett.* **91**, 169701 (2003); N. Gedik *et al.*, *Phys. Rev. Lett.* **91**, 169702 (2003).
 - [11] N. Gedik *et al.*, preprint cond-mat/0309121.
 - [12] N. Gedik *et al.*, *Science* **300**, 1410 (2003).
 - [13] E. J. Nicol and J. P. Carbotte, *Phys. Rev. B*, **67**, 214506 (2003).
 - [14] N. E. Booth, *Appl. Phys. Lett.* **50**, 293 (1987).
 - [15] D. Duffy, P. J. Hirschfeld and D. J. Scalapino, *Phys. Rev. B* **64**, 224522 (2001).
 - [16] M. B. Walker and M. F. Smith, *Phys. Rev. B* **61**, 11285 (2000).
 - [17] Y. Dagan, R. Krupke and G. Deutscher, *Phys. Rev. B* **62**, 146 (2000).
 - [18] M. Sutherland *et al.*, *Phys. Rev. B* **67**, 174520 (2003).